

## RAMTECH LABORATORIES, INC.

14104 ORANGE AVENUE PARAMOUNT, CALIFORNIA 90723-2019 • TELEPHONE (562) 633-4824 • FAX (562) 633-4128

Eugene Levin  
NeoPoxy Corporation  
6805 Sierra Court, Suite A  
Dublin, CA 94568-2654

July 19, 2000

Reissued: January 25, 2002 & July 10, 2003  
Company and Product Name Change Only

Laboratory Number 11474C-99

RE: Chemical Resistance Testing on (NPR-5300) Epoxy Liner

Dear Mr. Levin:

In accordance with your request, Ramtech Laboratories, Inc. conducted chemical resistance testing on (NPR-5300 Series) epoxy liner in accordance to ASTM D543 and the "Greenbook" 2000 Edition Standard Specifications for Public Works Construction Table 207 15.3 (B). The samples were weighed at intervals of 28, 56, 84, and 112-day exposures.

**Conditions of Acceptance:**

No weight gain or weight loss greater than  $\pm 1\%$ .

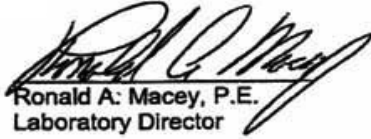
**Results:**

To the extent tested the samples meet the minimum requirements of Table 207-15.3 (A) for weight change requirements.

The results are shown on the following page.

Respectfully Submitted:

Ramtech Laboratories, Inc.

  
Ronald A. Macey, P.E.  
Laboratory Director

Ramtech Laboratories, Inc. reports are for the exclusive use of the client to whom they are addressed. Permission is granted to reproduce this report provided it is reproduced in its entirety. The use of the name Ramtech Laboratories, Inc. in any advertising or related materials must have prior written approval. Reports apply only to samples tested and are not necessarily indicative of the quality of apparently identical or similar products. Ramtech Laboratories, Inc. is a recognized Test Laboratory with the City of Los Angeles (RR 23840) and the ICBO Evaluation Service, Inc. (TL-187)

ENGINEERING • MATERIALS TESTING

**RAMTECH LABORATORIES, INC.**

14104 ORANGE AVENUE PARAMOUNT, CALIFORNIA 90723-2019 • TELEPHONE (562) 633-4824 • FAX (562) 633-4128

<b>Chemical Solution</b>	<b>Percent Wt. Change</b>
Sulfuric Acid, 31%	0.303
Sodium Hydroxide, 5%	0.201
Ammonium Hydroxide, 5%	0.263
Nitric Acid, 1%	0.375
Ferric Chloride, 1%	0.261
Sodium Hypochlorite, 1%	-0.456
Soap, 0.1%	0.251
Detergent, 0.1%	0.242
Bacteriological, BOD 700 ppm	0.252

Ramtech Laboratories, Inc. reports are for the exclusive use of the client to whom they are addressed. Permission is granted to reproduce this report provided it is reproduced in its entirety. The use of the name Ramtech Laboratories, Inc. in any advertising or related materials must have prior written approval. Reports apply only to samples tested and are not necessarily indicative of the quality of apparently identical or similar products. Ramtech Laboratories, Inc. is a recognized Test Laboratory with the City of Los Angeles (RR 23840) and the ICBO Evaluation Service, Inc. (TL-187)

**ENGINEERING • MATERIALS TESTING**